

Tăng cường khả năng ứng dụng chất nền carbon từ vỏ chuối kết hợp với g-C₃N₄ làm chất quang xúc tác xử lý môi trường

Phan Thị Thùy Trang^{1,*}, Trương Thanh Tâm¹,
Mai Thị Tường Vy², Nguyễn Thị Lan^{1,*}

¹Khoa Khoa học Tự nhiên, Trường Đại học Quy Nhơn, Việt Nam
²Phòng hành chính - Tổng hợp, Trường Đại học Quy Nhơn, Việt Nam

Ngày nhận bài: 28/09/2023; Ngày sửa bài: 14/11/2023;
Ngày nhận đăng: 01/12/2023; Ngày xuất bản: 28/02/2024

TÓM TẮT

Chất xúc tác quang carbon/g-C₃N₄ (BC/CN) được tổng hợp thành công bằng phương pháp nung đơn giản từ tiền chất carbon (tổng hợp từ vỏ chuối) và urea. Hoạt tính quang xúc tác và độ bền của vật liệu BC/CN được đánh giá qua sự phân hủy dung dịch RhB dưới vùng ánh sáng khả kiến. Ảnh hưởng của hàm lượng carbon trong composite trên hoạt tính xúc tác đã được khảo sát. Kết quả cho thấy hiệu suất quang xúc tác của composite BC/CN cao hơn g-C₃N₄ (CN) tinh khiết và so với các vật liệu composite ở các tỷ lệ khác. Điều này cho thấy vật liệu BC/CN-150 có độ bền quang xúc tác dưới vùng ánh sáng khả kiến. Kết quả này sẽ cung cấp cái nhìn mới về việc điều chế các chất xúc tác quang có hiệu quả cao trên nền g-C₃N₄.

Từ khóa: Carbon, g-C₃N₄, chất xúc tác quang, rhodamine B, vỏ chuối.

*Tác giả liên hệ chính.

Email: phanthithuytrang@qnu.edu.vn; nguyenthilan@qnu.edu.vn

Enhance the applicability of carbon substrates from banana peels combined with g-C₃N₄ as a photocatalyst for environmental treatment

Phan Thi Thuy Trang^{1,*}, Truong Thanh Tam¹,
Mai Thi Tuong Vy², Nguyen Thi Lan^{1,*}

¹Faculty of Natural Sciences, Quy Nhon University, Vietnam

²Administrative - General Office, Quy Nhon University, Vietnam

Received: 28/09/2023; Revised: 14/11/2023;

Accepted: 01/12/2023; Published: 28/02/2024

ABSTRACT

Carbon/g-C₃N₄ photocatalyst (BC/CN) was successfully prepared by a simple calcination method from carbon precursor (synthesized from waste banana peels) and urea. The activity and stability of BC/CN were evaluated by rhodamine B (RhB) degradation under visible light. The influence of carbon content in the composite on catalytic activity was studied. The results show that the photocatalytic efficiency of the BC/CN composite is higher than that of the g-C₃N₄ (CN) pristine and the rate constant of the BC/CN-150 sample is higher than the other samples. This shows that BC/CN-150 material has photocatalytic stability under the visible light region. This process will provide new insight into preparing highly efficient g-C₃N₄-based photocatalysts.

Keywords: Carbon, g-C₃N₄, photocatalyst, rhodamine B, banana peels.

1. INTRODUCTION

Photocatalysis, with many outstanding advantages, has become a subject of extensive research by scientists for application in treating toxic organic compounds in water. Recently, graphitic carbon nitride (g-C₃N₄) has exhibited great potential to be applied in visible light photocatalysis.¹ This material has many advantages, such as having a narrow bandgap energy (about 2.7 eV), high surface area, and unique morphology. However, g-C₃N₄ has a high photogenerated electron-hole pair recombination rate, which reduces the photocatalytic efficiency of the material. Many methods have been proposed to adjust the morphological structure

and surface chemical state of g-C₃N₄ to improve the photocatalytic efficiency of the material. One of the most used methods is to combine with other materials to create composites such as MoS₂,² WO₃,³ and SnS₂.⁴

Carbon materials with sp² hybridized π bonds can suppress photogenerated electron-hole recombination and improve the utilization of visible light when combined with other photocatalysts.⁵ Specifically, the research group of Ong et al.⁶ synthesized reduced graphene oxide (rGO)/g-C₃N₄ material through electrical interaction. With the excellent electrical conductivity and high electron storage capacity of graphene, photogenerated electrons transfer

*Corresponding author.

Email: phanthithuytrang@qnu.edu.vn; nguyenthilan@qnu.edu.vn

from $g\text{-C}_3\text{N}_4$ to rGO through an osmosis mechanism to improve the efficiency of CO_2 reduction into CH_4 by photocatalysis. Gu and his colleagues⁷ synthesized rGO/ $g\text{-C}_3\text{N}_4$ material by microwave method from GO and melamine precursors. The results showed that the existence of rGO did not disrupt the structure of $g\text{-C}_3\text{N}_4$. The rate of decomposition of rhodamine B is 2.86 times that of $g\text{-C}_3\text{N}_4$ under visible light; this may be due to the more effective photogenerated electron-hole separation of the composite due to the synergistic effect of rGO and $g\text{-C}_3\text{N}_4$.

Therefore, carbon is an ideal material to manufacture carbon/ $g\text{-C}_3\text{N}_4$ composites for use as photocatalysts. Besides, the surface of activated carbon is a lot of carboxyl, phenolic hydroxyl, carbonyl, lactone, and amide groups, which can chemically react with polymers to form composites. Furthermore, activated carbon synthesized from by-product biomass materials has partly helped reduce environmental pollution. Making effective use of banana peels is also beneficial for reducing resource waste.

In this study, banana peels waste was used as a biological pretreatment agent to produce activated carbon through calcination. Then, the carbon/ $g\text{-C}_3\text{N}_4$ composite was obtained by calcination from the carbon and $g\text{-C}_3\text{N}_4$ precursors. Various characterizations were conducted to clarify the structure and morphology of the synthesized material. Then, an efficient, economical, and environmentally friendly photocatalytic method is used to remove rhodamine B in wastewater.

2. EXPERIMENTAL SECTION

2.1. Material synthesis

Chemicals: All chemicals for materials synthesis include banana peel, urea, KOH 20%, HCl 2 M, $\text{C}_2\text{H}_5\text{OH}$, H_2O_2 , and rhodamine B (China).

Materials synthesis: Banana peels were washed with deionized water to remove dirt and cut into small pieces while still fresh. Then, it was dried in a vacuum environment for 24 hours at 110 °C. The dry shell was finely ground and

calcined in an Argon gas at 800 °C for 5 hours, and the heating rate is 5 °C/min. Then, the obtained product is further treated with KOH 20% solution at 70 °C for 2 hours and HCl 2 M solution at 60 °C for 15 hours. The obtained product is filtered, washed, and dried in a vacuum environment at 110 °C for 12 hours. Next, the product is calcined in air at 300 °C for 3 hours. After calcination, the product is filtered, washed with HCl 2 M solution and water, and dried to obtain the product activated carbon from banana peel, denoted BC.

The mixture of urea (20 g) with BC (0.1 g) was dispersed into 50 ml of water and alcohol solution and stirred continuously at a temperature of 60 °C until completely dry. Grind the solid amount finely and calcine in the Argon gas at 550 °C for 1 hour. The solid was filtered, washed, and dried at 80 °C for 12 hours to obtain the C/ $g\text{-C}_3\text{N}_4$ composite (symbolized as BC/CN). For comparison, the material $g\text{-C}_3\text{N}_4$ was also synthesized similarly to the above conditions but without the presence of activated carbon (symbolized as CN).

2.2. Material characterization

X-ray diffraction spectra of the samples were measured on a Bruker D2 Advance diffractometer with a Cu X-ray tube with wavelength λ ($\text{CuK}\alpha$) = 1.5406 Å, power 40 kV, current 40 mA. Scanning angle from 10 to 80°. Infrared spectra were recorded on an IRAffinity-1S spectrometer (Shimadzu) with wavenumbers ranging from 400 to 4000 cm^{-1} . The composition of the element was determined by EDS spectroscopy. UV-Vis-DRS spectra of material samples were determined on a Jasco-V770 machine with wavelengths from 200 - 800 nm. TEM images were measured on a JEOL JEM-2100F.

2.3. Photocatalytic properties

The photocatalytic activity of the material was determined through the decomposition reaction of RhB in aqueous solution under visible light. Add 50 mg of catalyst into 100 mL of RhB solution with a concentration of 10 mg/L and

stir in the dark for 1 hour to achieve adsorption-desorption equilibrium. Then, proceed with the photocatalytic process with a 30W LED lamp. Every 10 minutes, take 5 mL of the solution and centrifuge, removing the solid part. The concentration of RhB in the solution was determined on a UV-Vis meter (CE-2011) at a wavelength of 553 nm.

3. RESULTS AND DISCUSSION

3.1. Material characteristics

Characteristic results of the crystal structure of materials BC, CN, and BC/CN- x ($x=100, 150$, and 200) were investigated by X-ray diffraction spectrum, and the results are shown in Figure 1.

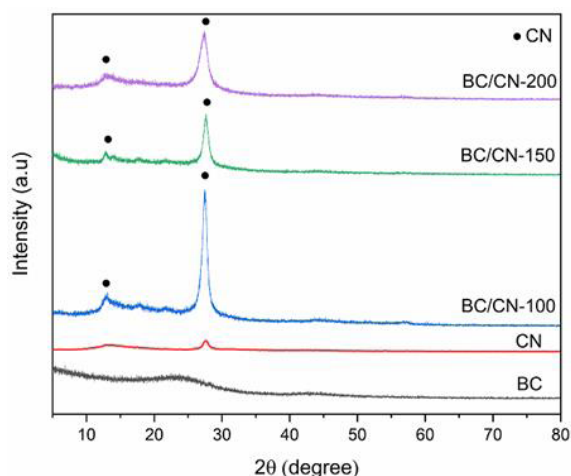


Figure 1. XRD patterns of BC, CN, and BC/CN- x ($x = 100; 150; 200$).

The results in Figure 1 show that the BC sample has a raised area in the value range $2\theta = 20\text{--}30^\circ$, which is characteristic of the amorphous structure of activated carbon.⁸ The CN sample has a diffraction peak at $2\theta = 13.2^\circ$ and 27.5° due to the layered structure of $g\text{-C}_3\text{N}_4$ with alternating stacking of conjugated aromatic units similar to the structure of graphite.⁹ In the BC/CN- x composite, all the peaks of $g\text{-C}_3\text{N}_4$ appeared, but no peaks of the BC sample were seen. This may be due to the overlap of carbon layers between $g\text{-C}_3\text{N}_4$ crystals by composite formation.

The chemical bond characteristics of the samples were characterized by FT-IR spectroscopy. The results are shown in Figure 2.

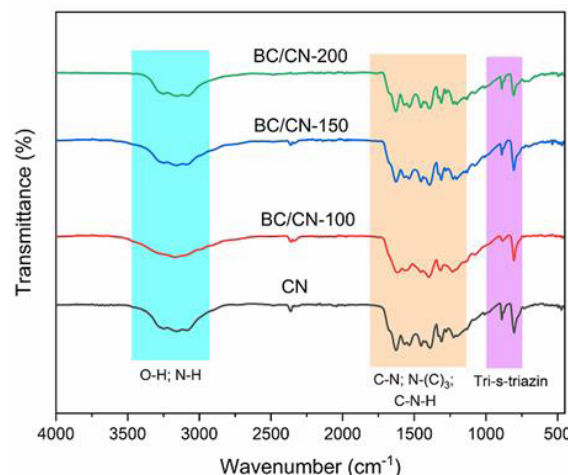


Figure 2. FT-IR spectra of CN and BC/CN- x ($x = 100; 150; 200$).

For the CN sample, the intensity band at 809.6 cm^{-1} shows the typical characteristic structure of tri-s-triazine.¹⁰ Bands at 1635.1 , 1570.8 , and 1418.3 cm^{-1} are assigned to the aromatic C-N vibration. The bands at 1324.6 and 1254.9 cm^{-1} are assigned to the stretching vibrations of the bonded blocks of fully condensed N-(C)_3 and partially condensed C-N-H, respectively.¹¹ Absorbance in the range of $3200\text{--}3400\text{ cm}^{-1}$ is related to residual N-H groups and O-H bands.¹² Thereby, it is seen that there is no obvious change between the CN and the BC/CN- x , which shows that the presence of amorphous carbon does not change the structure of $g\text{-C}_3\text{N}_4$.

The structures of BC, CN, and BC/CN composite are characterized by TEM images shown in Figure 3.

The TEM image of the BC sample (Figure 3a) shows a complex structure with defective graphene layers. The CN material (Figure 3b) has a morphology similar to a 2D nanosheet with a thin layer structure. However, compared to the 2D layered sheets of CN, the BC/CN (Figure 3c) shows stacked layers. This can be amorphous carbon materials grown on CN to form composites with surfaces in close contact with each other by heat treatment. The EDX spectrum of the composite shows the full elemental compositions of C and N (Figure 3d).

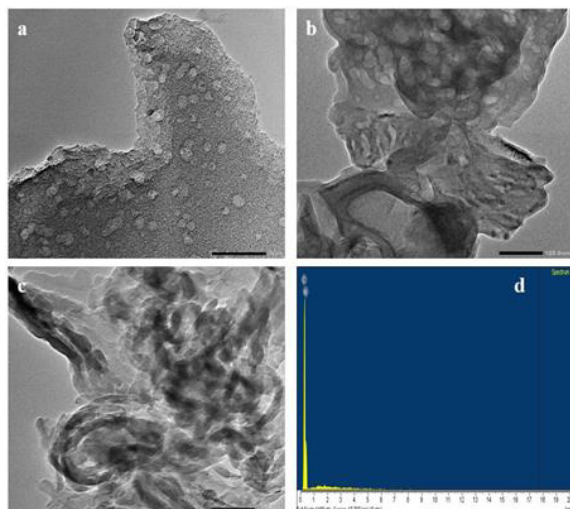


Figure 3. TEM image of BC (a), CN (b), BC/CN-150 (c), and EDX of BC/CN-150 (d).

To determine the photoelectric properties of CN and BC/CN-x composite, UV-Vis diffuse reflectance spectra were performed in Figure 4.

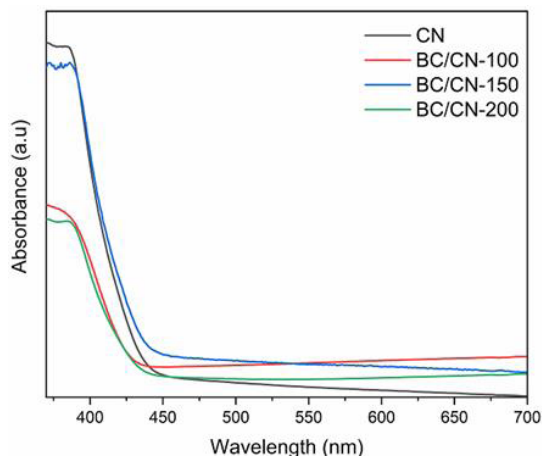


Figure 4. UV-vis diffuse reflectance spectra of CN; BC and BC/CN-x composite.

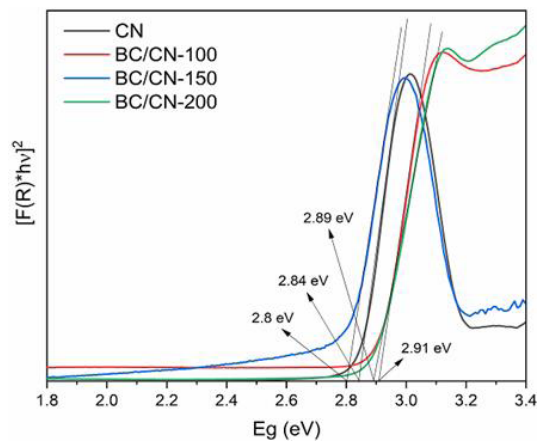


Figure 5. Band gap energy of CN and BC/CN-x composite.

The results show that the composite, after combining with amorphous carbon has a higher absorption intensity over the wavelength range investigated. This is clearly shown in Figure 5 about the band gap of the material. In which the band gap of BC/CN-150 sample ($E_g=2.8$ eV) has a smaller value than the two other samples BC/CN-100 ($E_g=2.89$ eV); BC/CN-200 ($E_g=2.91$ eV) and CN pure ($E_g=2.84$ eV).

3.2. Photocatalytic properties of materials

BC, CN, and BC/CN-x composites were investigated for their photocatalytic activity in decomposing RhB under visible light. The results are shown in Figure 6. Before evaluating the photocatalytic efficiency, the samples were adsorbed in the dark for 60 minutes to reach the adsorption-desorption balance.

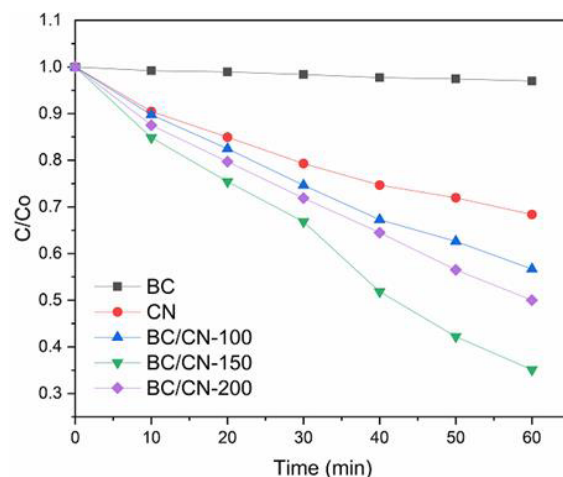


Figure 6. RhB decomposition under visible light of materials (reaction conditions = $10 \text{ mg} \cdot \text{L}^{-1}$ of RhB dye; 50 mg of catalyst weight; irradiation is LED light).

Figure 6 shows CN, BC/CN-100, BC/CN-150, and BC/CN-200 have an efficiency of 32%, 43.3%, 65%, and 50%, respectively. This shows that composite has higher photocatalytic efficiency than simple materials. This may be because BC material acts as an agent that increases the electrical conductivity and photo-adsorption capacity in the visible light region of the composite, demonstrated through the UV-Vis DRS spectrum (Figure 4) and E_g value (Figure 5). The laws of photocatalytic kinetics of materials all comply with the Langmuir-Hinshelwood model (Figure 7).

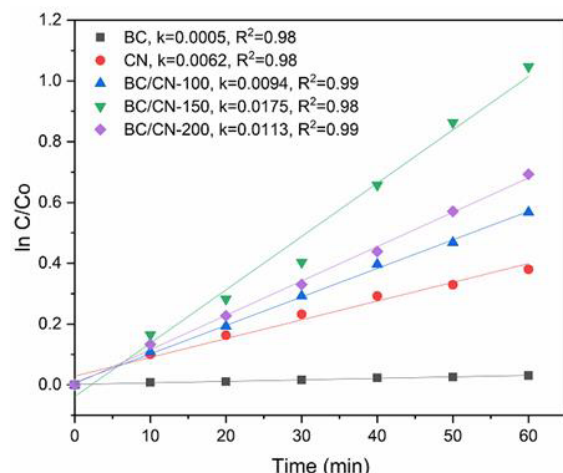


Figure 7. Kinetic fitting plot using the pseudo-first-order model of BC, CN, and BC/CN-x composite (reaction conditions = 10 mg. L⁻¹ of RhB dye; 50 mg of catalyst weight; irradiation is LED light).

4. CONCLUSION

BC/CN-x composite with different ratios were successfully synthesized via a simple reduction heating method in an Argon atmosphere from urea and carbon precursors. In particular, carbon materials are synthesized from waste biomass raw materials of banana peels. The photocatalytic activity of the composite material BC/CN-150 (H = 65%) is much higher than that of the g-C₃N₄ single (H = 32%) for the decomposition of RhB after 60 minutes of reaction under the visible light region. Therefore, this shows that the presence of carbon significantly improves the photocatalytic efficiency of the materials. This is a promising new research direction in utilizing waste as materials for wastewater treatment and minimizing environmental pollution.

REFERENCES

1. S. Kumaravel, C. Chandrasatheesh, G. Palanisamy, J. Lee, I. Hasan, S. Kumaravel, B. Avula, U. D. Pongiya, K. Balu. Highly efficient solar-light-active Ag-decorated g-C₃N₄ composite photocatalysts for the degradation of methyl orange dye, *Micromachines*, **2023**, *14*, 1454-1467.
2. T. H. Ha, N. T. M. Duyen, N. V. Phuc, N. T. Lan, P. T. T. Trang, H. Q. Dat, L. H. Hoang, K. J. Sung, V. Vien. One-pot synthesis of S-scheme MoS₂/g-C₃N₄ heterojunction as effective visible light photocatalyst, *Scientific Reports*, **2021**, *11*(1), 14787-14799.
3. J. Meng, J. Pei, Z. He, S. Wu, Q. Lin, X. Wei, J. Li, Z. Zhang. Facile synthesis of g-C₃N₄ nanosheets loaded with WO₃ nanoparticles with enhanced photocatalytic performance under visible light irradiation, *RSC Advances*, **2017**, *7*(39), 24097-24104.
4. N. T. T. Huong, T. H. Ha, N. P. Hung, N. V. Phuc, L. Q. Dai, N. T. Lan, P. T. T. Trang, V. Vien. A facile synthesis of SnS₂/g-C₃N₄ S-scheme heterojunction photocatalyst with enhanced photocatalytic performance, *Journal of Science: Advanced Materials and Devices*, **2022**, *7*(2), 100402-100410.
5. Q. Xu, B. Cheng, J. Yu, G. Liu. Making co-condensed amorphous carbon/g-C₃N₄ composites with improved visible-light photocatalytic H₂-production performance using Pt as cocatalyst, *Carbon*, **2017**, *118*, 241-249.
6. W. J. Ong, L. L. Tan, S. P. Chai, S. T. Yong, A. R. Mohamed. Surface charge modification via protonation of graphitic carbon nitride (g-C₃N₄) for electrostatic self-assembly construction of 2D/2D reduced graphene oxide (rGO)/g-C₃N₄ nanostructures toward enhanced photocatalytic reduction of carbon dioxide to methane, *Nano Energy*, **2015**, *13*, 757-770.
7. Y. Gu, Y. Yu, J. Zou, T. Shen, Q. Xu, X. Yue, J. Meng, J. Wang. The ultra-rapid synthesis of rGO/g-C₃N₄ composite via microwave heating with enhanced photocatalytic performance, *Materials Letters*, **2018**, *232*, 107-109.
8. T. V. Thuan, B. T. P. Quynh, T. D. Nguyen, V. T. T. Ho, L. G. Bach. Response surface methodology approach for optimization of Cu²⁺, Ni²⁺ and Pb²⁺ adsorption using KOH-activated carbon from banana peel, *Surfaces and Interfaces*, **2017**, *6*, 209-217.
9. M. R. Islam, A. K. Chakraborty, M. A. Gafur, M. A. Rahman, M. H. Rahman. Easy preparation of recycle thermally stable visible-light-active graphitic-C₃N₄/TiO₂ nanocomposite photocatalyst for efficient decomposition

- of hazardous organic industrial pollutions in aqueous medium, *Research on Chemical Intermediates*, **2019**, *45*, 1753-1773.
10. J. Liu, T. Zhang, Z. Wang, G. Dawson, W. Chen. Simple pyrolysis of urea into graphitic carbon nitride with recyclable adsorption and photocatalytic activity, *Journal of Materials Chemistry*, **2011**, *21*(38), 14398-14401.
 11. X. Du, G. Zou, Z. Wang, X. Wang. A scalable chemical route to soluble acidified graphitic carbon nitride: an ideal precursor for isolated ultrathin g-C₃N₄ nanosheets, *Nanoscale*, **2015**, *7*(19), 8701-8706.
 12. X. She, L. Liu, H. Ji, Z. Mo, Y. Li, L. Huang, D. Du, H. Xu, H. Li. Template-free synthesis of 2D porous ultrathin nonmetal-doped g-C₃N₄ nanosheets with highly efficient photocatalytic H₂ evolution from water under visible light, *Applied Catalysis B: Environment and Energy*, **2016**, *187*, 144-153.